

Title: High Density Polyethylenes Bearing Isolated In-Chain Carbonyls

Authors: Shan Tang, Falk William Seidel, Kyoko Nozaki

This is the peer reviewed version of the following article: [S. Tang, F. W. Seidel, K. Nozaki, *Angew. Chem. Int. Ed.* 2021, 60, 26506.], which has been published in final form at [<https://doi.org/10.1002/anie.202110957>]. This article may be used for non-commercial purposes in accordance with Wiley Terms and Conditions for Use of Self-Archived Versions. This article may not be enhanced, enriched or otherwise transformed into a derivative work, without express permission from Wiley or by statutory rights under applicable legislation. Copyright notices must not be removed, obscured or modified. The article must be linked to Wiley's version of record on Wiley Online Library and any embedding, framing or otherwise making available the article or pages thereof by third parties from platforms, services and websites other than Wiley Online Library must be prohibited.

To be cited as: *Angew. Chem. Int. Ed.* 2021, 60, 26506.

Link to VoR: <https://doi.org/10.1002/anie.202110957>

High Density Polyethylenes Bearing Isolated In-Chain Carbonyls

Shan Tang,[†] Falk William Seidel,[†] and Kyoko Nozaki*

[*] Dr. S. Tang,[†] Dr. F. W. Seidel,[†] Prof. Dr. K. Nozaki
 Department of Chemistry and Biotechnology, Graduate School of Engineering, The University of Tokyo, 7-3-1- Hongo, Bunkyo-ku, Tokyo 113-8656 (Japan)

E-mail: nozaki@chembio.t.u-tokyo.ac.jp

[†] These authors contributed equally to this work.

Supporting information for this article is given via a link at the end of the document.

Abstract: Polyethylene materials are highly important polymers which are produced in the largest volume among all plastics. Due to the chemical inert property of saturated carbon-carbon bonds, the degradation of polyethylene is extremely challenging, which prevents them from efficient chemical recycling. Installing functional groups in the main chain of polyethylenes may facilitate the degradation and following chemical recycling of polyethylene materials. Here we report a highly selective approach for the synthesis of high density polyethylenes bearing low content isolated in-chain carbonyls. Linear high-molecular weight polyethylene chains are synthesized via the palladium catalyzed copolymerization of ethylene with metal carbonyls. Different from traditional ethylene/CO copolymerization reactions, excellent non-alternating selectivity has been achieved. While the properties of polyethylene have been retained in the copolymer, faster degradation compared with that of polyethylene was observed upon UV light irradiation. The synthesized materials may therefore serve as more environmentally friendly alternative plastics than traditional polyethylene materials.

Polyolefin plastics are fundamental materials, which have been used in numerous areas of modern society. Specifically, polyethylene plastics are produced in the largest amount in volume among all polymer materials,^[1-2] but their remarkable chemical inertness has led to serious environmental plastic pollution issues (Figure 1a).^[3-4] Accordingly, efficient chemical recycling of polyolefins became an emerging hot topic.^[5-6] One potential solution to overcome the problem of the high chemical inertness of polyethylene plastics is to install a small amount of cleavable functional groups in the main chain of polyethylenes.^[7] It is known that in-chain carbonyl units can enable chain scission through Norrish-type photochemical reactions.^[8-10] Since the 1950s, radical copolymerization of ethylene and carbon monoxide (CO) to yield low-density polyketone materials was developed providing either alternating or ethylene rich non-alternating copolymers both with branched structures.^[11-12] Later, the coordination-insertion copolymerization using group 10 metal complexes was developed to give completely alternating linear copolymers.^[13-14] The high content of carbonyl groups alters the physical property of these materials in a way in which they do not serve as an alternative to polyethylene plastics (Figure 1b).^[15-17] Consequently, efforts have been paid to develop methods for synthesizing polyethylenes with a low-content of carbonyl groups that would allow to retain the bulk material properties of polyethylene while adding further functionality such as photodegradability.^[18-24] Especially the so far unachieved spread-out incorporation of the carbonyl groups into the polymer chain is highly desired over accumulated alternating structural units in

order to maximize the breakdown of the polymer chains into smaller pieces (Figure 1c).

Nearly twenty years ago, Drent *et al.* reported the palladium catalyzed synthesis of modestly non-alternating copolymers of ethylene and CO by employing a phosphine sulfonate (P/S) ligand (up to 18.4 mol% extra ethylene units with 40.8 mol% CO content).^[18] While later studies by the groups of Sen and Müller employing monomer feeds with high ethylene-to-CO ratio could further lower the CO incorporation down to 1.5 mol%,^[22, 25] a clustering of the CO units in the polymer chain remained so far mechanistically unavoidable due to formation of a strong chelate after CO insertions (Figure 1d).^[20, 26] More recently, the group of Mecking reported a radical copolymerization strategy for the synthesis of highly branched polyethylenes with low content in-chain carbonyl groups.^[23] While a high selectivity towards isolated carbonyls was achieved, compared to coordination-insertion copolymerization, much higher initial ethylene pressures (> 300 bar) were required for the successful radical copolymerization.

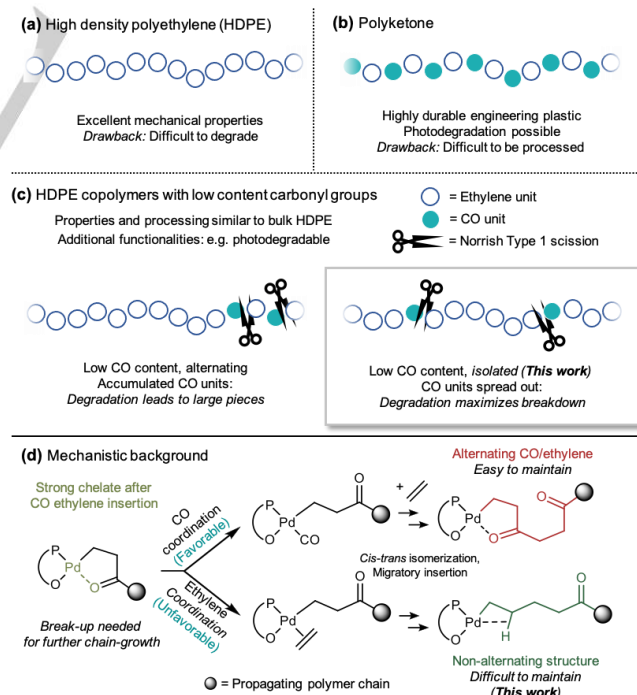


Figure 1. Background of ethylene/CO copolymerization.

Previously reported methods for the non-alternating ethylene/CO copolymerization generally led to the formation of

COMMUNICATION

polyethylenes containing both isolated and alternating carbonyl groups with low selectivities,^[18-23] while the incorporation of CO often lowered the molecular weights of the obtained polymers.^[22] Here we aimed at improving of both the selectivity for isolated CO insertion and molecular weight of the non-alternating ethylene/CO copolymers for practical applications of these materials as potential environmentally friendly plastics. Intriguingly metal carbonyls, which are industrially produced in the context of metal refinement by transport reactions, have been used as alternative CO sources in transition metal catalyzed carbonylation reactions^[27-29] Compared with color- and odorless CO gas, metal carbonyls are generally solids or liquids, which makes them safer and easier to handle in ethylene copolymerization. Thus, we wondered whether metal carbonyls could be used as a CO source for accessing polyethylenes with low contents of in-chain carbonyl groups.

Different metal carbonyls were tested as comonomers in the polymerization of ethylene using a common palladium phosphine-sulfonate (P/S) catalyst, **[Pd]-1** (Table 1, entries 1-4). When Fe₂(CO)₉, Mn₂(CO)₁₀ and Fe(CO)₅ were used as the CO sources (Bond enthalpies of metal carbonyls were discussed in Table S1, supporting information), polymers were obtained after precipitation with MeOH and washing with diluted hydrochloric


acid to remove metal residues. ¹H and ¹³C{¹H} NMR analysis of the obtained polymers clearly supported the presence of carbonyl groups in the polyethylene main-chain. The ¹H NMR spectrum of the copolymer corresponding to entry 1 (Figure 1a) showed a characteristic triplet of the isolated ketone unit at $\delta = 2.42$ ppm (**B**), which was also observed at 210.5 ppm (**A**) in the ¹³C{¹H} NMR spectrum (Figure 2b). A weak signal for alternating ketone unit was found at $\delta = 2.70$ ppm (s; **H**) in the ¹H NMR spectrum (Figure 2a). The highest CO incorporation ratio (1.6 mol%, corresponding to about 2.3 ketone units per chain) was observed with Fe₂(CO)₉ for which in-chain isolated carbonyls were observed as the predominant insertion moiety [Isolated carbonyls/Alternating carbonyls (I/A) = 96:4]. The choice of metal carbonyls had a significant effect on the incorporation of CO. Significantly lower CO incorporation ratios were observed in the case of Fe(CO)₅ and Mn₂(CO)₁₀ (0.16 and 0.14 mol% respectively), while almost no alternating carbonyls were observed in the obtained copolymer and the polymer yields and molecular weights were increased in comparison to the copolymer in entry 1 (Table 1, entries 2 and 3). No polymer was obtained when Co₂(CO)₈ was employed as the comonomer, which was likely due to the catalyst deactivation by Co₂(CO)₈ (Table 1, entry 4).

Table 1. Copolymerization of ethylene with metal carbonyls using palladium complexes^[a]

Entry	cat. [Pd]	M _x (CO) _y (mmol)	Temp. (°C)	Yield (g) ^[b]	Activity (g·mmol ⁻¹ ·h ⁻¹)	M _n (Kg/mol) ^[c]	M _w /M _n ^[c]	i. r. (%) ^[d]	I/A ^[e]
1	[Pd]-1	Fe ₂ (CO) ₉ (0.25)	80	0.115	3.8	4.0	1.5	1.6	96:4
2	[Pd]-1	Fe(CO) ₅ (0.50)	80	1.609	54	14	2.1	0.16	>99:1
3	[Pd]-1	Mn ₂ (CO) ₁₀ (0.25)	80	0.638	21.3	14	2.0	0.14	>99:1
4	[Pd]-1	Co ₂ (CO) ₈ (0.25)	80	N.D.	N.A.	N.A.	N.A.	N.A.	N.A.
5	[Pd]-1	Fe ₂ (CO) ₉ (0.25) ^[f]	80	1.226	40.9	3.4	5.3	<0.01	N.A.
6	[Pd]-1	CO (ca. 0.25) ^[g]	80	1.078	35.9	2.4	6.1	0.31	67:33
7	[Pd]-1	Fe ₂ (CO) ₉ (0.10)	80	0.195	6.5	5.0	1.4	1.1	99:1
8	[Pd]-1	Fe ₂ (CO) ₉ (0.50)	80	0.058	1.9	2.9	1.9	3.1	91:9
9	[Pd]-2	Fe ₂ (CO) ₉ (0.25)	80	0.230	7.7	4.1	1.9	0.83	>99:1
10	[Pd]-3	Fe ₂ (CO) ₉ (0.25)	80	0.122	4.1	4.5	2.0	1.3	98:2
11	[Pd]-4	Fe ₂ (CO) ₉ (0.25)	60	0.189	6.3	26	1.5	0.24	>99:1
12	[Pd]-4	Fe ₂ (CO) ₉ (0.25)	80	0.436	14.5	58	2.0	0.41	>99:1
13	[Pd]-4	Fe ₂ (CO) ₉ (0.25)	100	0.391	13.0	44	2.2	0.58	99:1
14	[Pd]-5	Fe ₂ (CO) ₉ (0.25)	80	0.090	3.0	17	1.7	<0.05	N.A.
15	[Pd]-6	Fe ₂ (CO) ₉ (0.25)	80	0.740	24.5	47	2.4	<0.02	N.A.
16 ^[h]	[Pd]-1	Fe ₂ (CO) ₉ (0.25)	80	0.036	1.2	3.7	2.3	3.9	90:10

[a] A mixture of the catalyst (10 μ mol) and M_x(CO)_y in toluene (10 mL) was stirred in a glass tube under an ethylene atmosphere (3.0 MPa) for 3 h in a 50 mL autoclave. [b] Yields of isolated product after precipitation with methanol (80 mL). N.D. = not detected. [c] Molecular weights determined by size-exclusion chromatography using polystyrene standards corrected by universal calibration. [d] CO incorporation ratio (i. r.) in mol% determined by ¹H NMR analysis. [e] The I/A ratio was determined by ¹H NMR analysis. I/A = Isolated carbonyls/Alternating carbonyls. [f] Fe₂(CO)₉ was added outside the glass tube along with toluene (1.0 mL). [g] Ethylene containing about 0.3 mol% CO was used. [h] 1.0 MPa of ethylene was used. Dip = 2,6-diisopropylphenyl; Lut = 2,6-lutidine.

COMMUNICATION

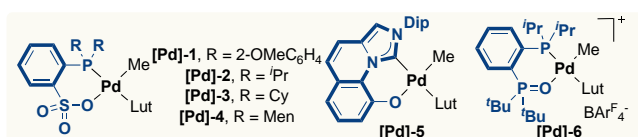

Control experiments were carried out to confirm an interaction between the palladium catalyst and metal carbonyls. When $\text{Fe}_2(\text{CO})_9$ was added outside the glass tube in the reaction autoclave, a high yield of polymer was obtained while less than 0.01 mol% CO incorporation was observed (Table 1, entry 5). When CO gas was used as the carbonylation source instead of metal carbonyls, a copolymer was obtained in a high yield but with a low molecular weight and poor PDI (Table 1, entry 6). Though with a low CO incorporation ratio (0.31 mol%), a poor selectivity of isolated over alternating carbonyl units was observed (I/A = 67:33), which was in stark contrast to the experiments employing metal carbonyls as a CO source. A stoichiometric experiment was then performed to further confirm the CO transfer from $\text{Fe}_2(\text{CO})_9$ to **[Pd]-1** (Figure 3). As was expected, slow CO insertion to **[Pd]-1** was observed after mixing an excess amount of $\text{Fe}_2(\text{CO})_2$ with **[Pd]-1** at room temperature (see supporting information, Figure S1).

Next, the effect of different reaction parameters on the copolymerization were explored. Decreasing the amount of $\text{Fe}_2(\text{CO})_9$ lowered the CO incorporation ratio but increased CO insertion selectivity and molecular weight of the copolymer (Table 1, entry 7). On the contrary, increasing the amount of $\text{Fe}_2(\text{CO})_9$ led to a high CO incorporation ratio but decreased molecular weight and CO insertion selectivity (Table 1, entry 8). Performing the copolymerization with $\text{Fe}_2(\text{CO})_9$ (0.25 mmol) under 1 MPa of ethylene afforded a copolymer with an even higher CO incorporation ratio (3.9 mol%) along with a higher molecular weight (Table 1, entry 16). First, palladium P/S complexes bearing different substituents on phosphine were tested. Similar molecular weights were observed in the case of **[Pd]-2** and **[Pd]-3** (Table 1, entries 9 and 10). Notably, **[Pd]-4** afford much higher molecular weights of the copolymer with an excellent selectivity toward non-alternating copolymerization (Table 1, entry 12). The effect of temperature on the copolymerization was investigated using **[Pd]-4** as the catalyst (Table 1, entries 11-13). Increasing the reaction temperature had a positive effect on the incorporation of CO, still the highest molecular weight (58 kg mol⁻¹, about 8 ketone units per chain) of the copolymer was obtained at 80 °C (Table 2, entry 12). According to ¹H NMR analysis, more than 99% selectivity towards the incorporation of isolated carbonyls was observed for this copolymer (Figure 2b). Trace amount of olefinic protons were detected, implying the possible chain-transfer via β -hydride elimination/ethylene re-insertion process (See SI, Figure S37, supporting information). The existence of only one carbonyl signal was confirmed by the ¹³C NMR analysis (Figure 2e). Analysis of metal residues in the copolymer by inductively coupled plasma atomic emission spectroscopy (ICP–AES) detected 0.03 wt% palladium and 0.19 wt% iron.

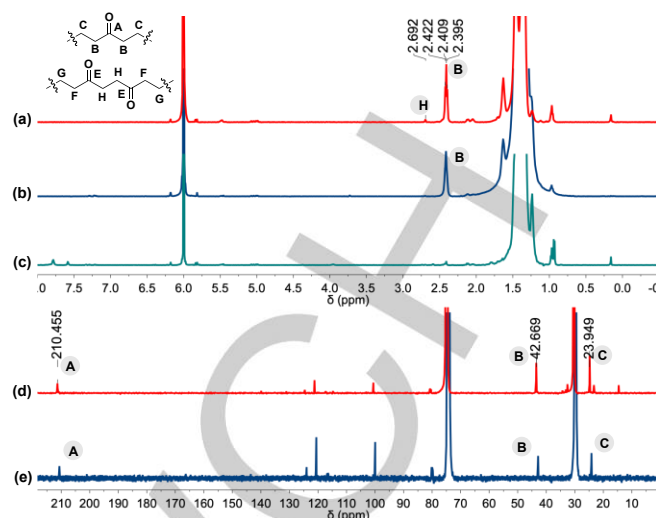


Figure 2. Assignment of characteristic NMR resonances. (a) ¹H NMR spectrum of the copolymer in Table 1, entry 1. (b) ¹H NMR spectrum of the copolymer in Table 1, entry 12. (c) ¹H NMR spectrum of the polymer in Table 1, entry 15. (d) ¹³C{¹H} NMR spectrum of the copolymer in Table 1, entry 1. (e) ¹³C{¹H} NMR spectrum of the copolymer in Table 1, entry 12.

Aside from the palladium P/S catalysts, a palladium NHC-phenolate (**[Pd]-5**) and a bisphosphine-monoxide catalyst (**[Pd]-6**) were tested under similar reaction conditions (Table 1, entries 14 and 15). Less than 0.05 mol% of CO incorporation was observed in the obtained polymers, which suggests that only high-density polyethylenes were obtained (See Figure 2c for the ¹H NMR spectrum of the polymer in Table 1, entry 15). It is known that diphosphine ligands such as dppp or dppb have been widely used in the palladium catalyzed alternating ethylene/CO copolymerization,^[13] but no polymer was obtained with both ligands when $\text{Fe}_2(\text{CO})_9$ was used as the carbonyl source (See supporting information for details). These results suggest that an interaction between the palladium P/S catalyst and the metal carbonyls are important for achieving the copolymerization, and that the metal carbonyls are crucial for allowing highly selective non-alternating ethylene/CO copolymerization. A plausible mechanism for CO transfer from $\text{Fe}_2(\text{CO})_9$ to **[Pd]-1** is presented in Figure S12, supporting information. First, disproportionation of $\text{Fe}_2(\text{CO})_9$ would lead to the formation of a 16-VE $\text{Fe}(\text{CO})_4$ and a 18-VE $\text{Fe}(\text{CO})_5$. Coordination of S=O units of the phosphine-sulfonate complexes to $\text{Fe}(\text{CO})_4$ would afford a more stable 18-VE species. At last, slow intramolecular CO transfer might take place at the nearby polymerization site. Based on the control experiments for thermal decomposition of $\text{Fe}_2(\text{CO})_9$ for slow CO release (Table 1, entry 5) and the experiment with CO gas (Table 1, entry 6), an interaction of the catalyst with the metal carbonyl precursors is likely to be the key for efficient incorporation of isolated CO units into the copolymers.

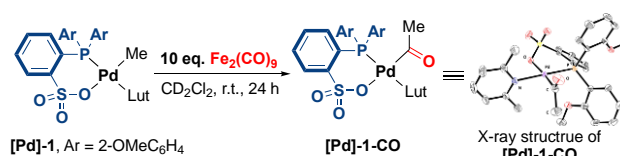


Figure 3. Stoichiometric experiment. CO transfer between **[Pd]-1** and $\text{Fe}_2(\text{CO})_9$.

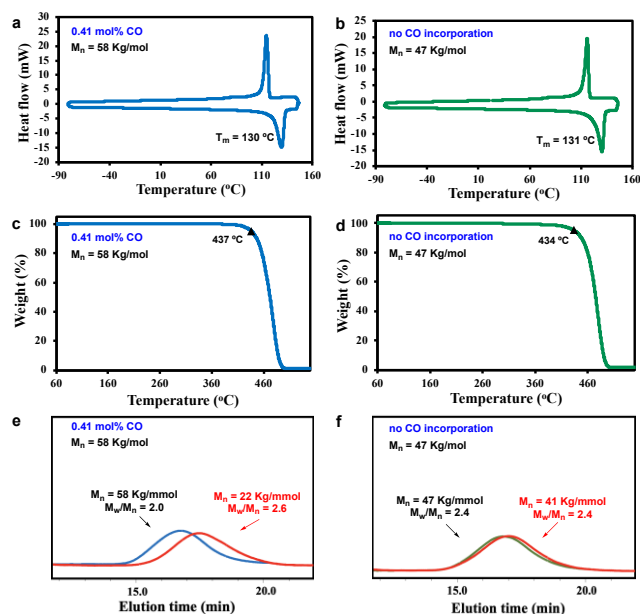


Figure 4. Comparison of the physical property between HDPE bearing in-chain isolated carbonyls and HDPE. (a) DSC trace of the copolymer in Table 1, entry 12 (0.41 mol% CO). (b) DSC trace of the polyethylene in Table 1, entry 15. (c) TGA curve of the copolymer in Table 1, entry 12 (0.41 mol% CO). (d) TGA curve of the polyethylene in Table 1, entry 15. (e) SEC trace of the copolymer in Table 1, entry 12 before (Blue line) and after (Red line) UV irradiation (275 nm at 30 °C for 50 h). (f) SEC trace of the polyethylene in Table 1, entry 15 before (Green line) and after (Red line) UV irradiation (275 nm at 30 °C for 50 h).

Differential scanning calorimetry (DSC) analysis of the copolymer in entry 12 in Table 1 revealed an endothermic peak at $T_m = 130$ °C (Figure 4a), closely resembling the HDPE obtained for entry 15 in Table 1 which showed an endothermic peak at $T_m = 131$ °C (Figure 4b). These results indicate the melt property of the copolymer is not compromised by the incorporation of a low quantity of CO. Moreover, the thermogravimetric analysis of the polymers in entry 12 and 15 gave similar results for $T_d = 437$ and 434 °C respectively (Figure 4c and 4d). The obtained copolymer is stable for thermal processing, which serves as another advantage in comparison with alternating polyketone materials. As a proof of concept, the photodegradability of the copolymer in Table 1, entry 12 was explored upon 275 nm UV light irradiation. The decomposition of the polyethylene in Table 1, entry 15 was also investigated under similar conditions to demonstrate the importance of low content CO incorporation. After irradiating the polymer at 30 °C for 50 h, the molecular weight of the copolymer (0.41 mol% CO incorporation) decreased significantly from 58 kg/mol to 22 kg/mol and the molecular weight distribution was broadened to $M_w/M_n = 2.6$ (Figure 4e). In the control experiment, only slight molecular weight change was observed, and the initial molecular weight distribution was maintained (Figure 4f). These results support our assumption that the incorporated low content carbonyl groups facilitate the degradation of polyethylene materials.

In conclusion, a highly selective reaction protocol for the synthesis of non-alternating, linear ethylene/CO copolymers has been developed. Incorporation of a low CO content in the main-chain of polyethylene along with remarkable isolated carbonyl selectivity was achieved via palladium catalyzed copolymerization of ethylene with metal carbonyls. This polyethylene copolymer retained the main physical properties of high density polyethylene,

while treating the obtained copolymer with UV light resulted in partial degradation. Therefore, the synthesized materials may serve as more environmentally friendly alternative plastics than traditional polyethylene materials.

Acknowledgements


We are grateful to Mr. Yuan Kang for his technical help in data collection. This work was supported by JSPS KAKENHI JP18H05259 and JST ERATO. F.W.S. was supported by a MEXT scholarship provided by the Ministry of Education, Culture, Sports, Science and Technology.

Keywords: high density polyethylene • non-alternating copolymerization • carbonyls • plastics • polymer degradation

- [1] R. Geyer, J. R. Jambeck, K. L. Law, *Sci. Adv.* **2017**, *3*, e1700782.
- [2] M. Stürzel, S. Mihan, R. Mülhaupt, *Chem. Rev.* **2016**, *116*, 1398.
- [3] J. R. Jambeck, R. Geyer, C. Wilcox, T. R. Siegler, M. Perryman, A. Andrady, R. Narayan, K. L. Law, *Science* **2015**, *347*, 768.
- [4] C. J. Moore, *Environ. Res.* **2008**, *108*, 131.
- [5] J. M. Garcia, M. L. Robertson, *Science* **2017**, *358*, 870.
- [6] J. Scheirs, W. Kaminsky, *Feedstock recycling and pyrolysis of waste plastics: converting waste plastics into diesel and other fuels*, John Wiley & Sons Incorporated, **2006**.
- [7] T. Zeng, W. You, G. Chen, X. Nie, Z. Zhang, L. Xia, C. Hong, C. Chen, Y. You, *iScience* **2020**, *23*.
- [8] G. H. Hartley, J. E. Guillet, *Macromolecules* **1968**, *1*, 165.
- [9] A. L. Andrady, *J. Appl. Polym. Sci.* **1990**, *39*, 363.
- [10] X. Wang, F. W. Seidel, K. Nozaki, *Angew. Chem. Int. Ed.* **2019**, *58*, 12955.
- [11] M. M. Brubaker, D. D. Coffman, H. H. Hoehn, *J. Am. Chem. Soc.* **1952**, *74*, 1509.
- [12] A. Sommazzi, F. Garbassi, *Prog. Polym. Sci.* **1997**, *22*, 1547.
- [13] E. Drent, P. H. M. Budzelaar, *Chem. Rev.* **1996**, *96*, 663.
- [14] K. Nozaki, S. Ito, in *Polymer Science: A Comprehensive Reference* (Eds.: K. Matyjaszewski, M. Möller), Elsevier, Amsterdam, **2012**, pp. 825.
- [15] C. Cheng, D. Guironnet, J. Barborak, M. Brookhart, *J. Am. Chem. Soc.* **2011**, *133*, 9658.
- [16] F. Garbassi, A. Sommazzi, L. Meda, G. Mestroni, A. Sciuotto, *Polymer* **1998**, *39*, 1503.
- [17] G. A. Holt Jr, J. E. Spruiell, *J. Appl. Polym. Sci.* **2002**, *83*, 2124.
- [18] E. Drent, R. van Dijk, R. van Ginkel, B. van Oort, R. I. Pugh, *Chem. Commun.* **2002**, 964.
- [19] A. K. Hearley, R. J. Nowack, B. Rieger, *Organometallics* **2005**, *24*, 2755.
- [20] R. Luo, D. K. Newsham, A. Sen, *Organometallics* **2009**, *28*, 6994.
- [21] L. Bettucci, C. Bianchini, C. Claver, E. J. G. Suarez, A. Ruiz, A. Meli, W. Oberhauser, *Dalton. Trans.* **2007**, 5590.
- [22] S. S. Soomro, D. Cozzula, W. Leitner, H. Vogt, T. E. Müller, *Polym. Chem.* **2014**, *5*, 3831.
- [23] (a) T. O. Morgen, M. Baur, I. Göttker-Schnetmann, S. Mecking, *Nat. Commun.* **2020**, *11*, 3693. (b) While our work was ongoing another paper from Mecking's group appeared as a preprint: <https://doi.org/10.26434/chemrxiv.14356796.v1>
- [24] S.-Y. Chen, R.-C. Pan, M. Chen, Y. Liu, C. Chen, X.-B. Lu, *J. Am. Chem. Soc.* **2021**.
- [25] D. K. Newsham, S. Borkar, A. Sen, D. M. Conner, B. L. Goodall, *Organometallics* **2007**, *26*, 3636.
- [26] A. Haras, A. Michalak, B. Rieger, T. Ziegler, *J. Am. Chem. Soc.* **2005**, *127*, 8765.
- [27] P. Nordeman, L. R. Odell, M. Larhed, *J. Org. Chem.* **2012**, *77*, 11393.
- [28] P. Baburajan, K. P. Elango, *Tetrahedron Lett.* **2014**, *55*, 1006.
- [29] J. T. Joseph, A. M. Sajith, R. C. Ningegowda, S. Shashikanth, *Adv. Synth. Catal.* **2017**, *359*, 419.

COMMUNICATION

Entry for the Table of Contents

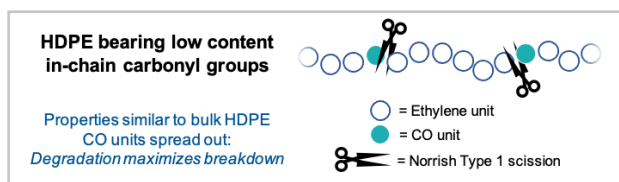

Incorporation of a low CO content in the main-chain of polyethylene along with remarkable isolated carbonyl selectivity was achieved via palladium catalyzed copolymerization of ethylene with metal carbonyls. This polyethylene copolymer retained the main physical properties of high-density polyethylene (HDPE), while treating the obtained copolymer with UV light resulted in partial degradation. Therefore, the synthesized materials may serve as more environmentally friendly alternative plastics than traditional polyethylene materials.